

Introduction

Moldflow software is widely used in injection molding simulation. Through the molding simulation, it is possible to know whether the thickness of the product is reasonable; whether the molding parameters are reasonable; whether the welding line position of the product exists in the area where the product strength is relatively weak; identify the area where the product air pockets are concentrated; the time to reach the ejection temperature; whether the warpage deformation is within the tolerance, etc. Reasonable optimization for existing defects. Taking the battery cover of a digital camera as an example, this paper uses Moldflow software to analyze and optimize the warping deformation, optimize the position and number of glue ports through filling analysis, optimize the cooling system through cooling analysis, and optimize the cooling system through pressure-holding analysis. The packing parameters are optimized.

Product process analysis and pretreatment

The 3D model of the part is shown in Figure 1, the size of the product is: 192.2mm*104.1mm*50.7mm, and the volume is 60.05cm³. The processed model is exported in STL format, and then imported into Moldflow for meshing (dual-layer mesh) as shown in Figure 2. The repaired mesh statistics are shown in Figure 3. The number of meshes is 19277 triangular elements, the maximum aspect ratio is less than 10, and the matching rate is 94.4%, which fully meets the requirements of warpage analysis.

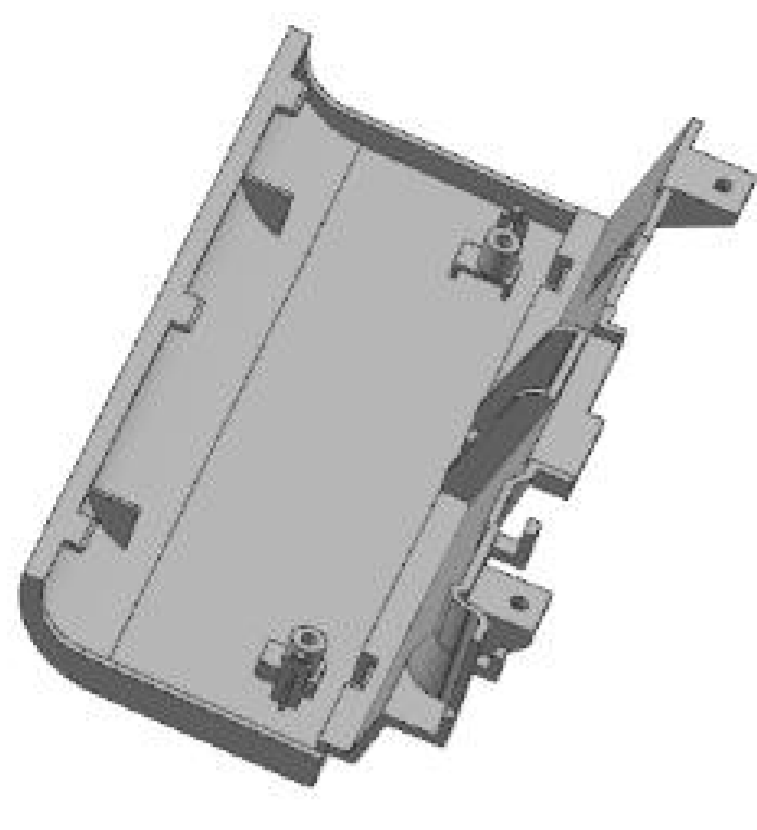


Figure 1. 3D model of the part

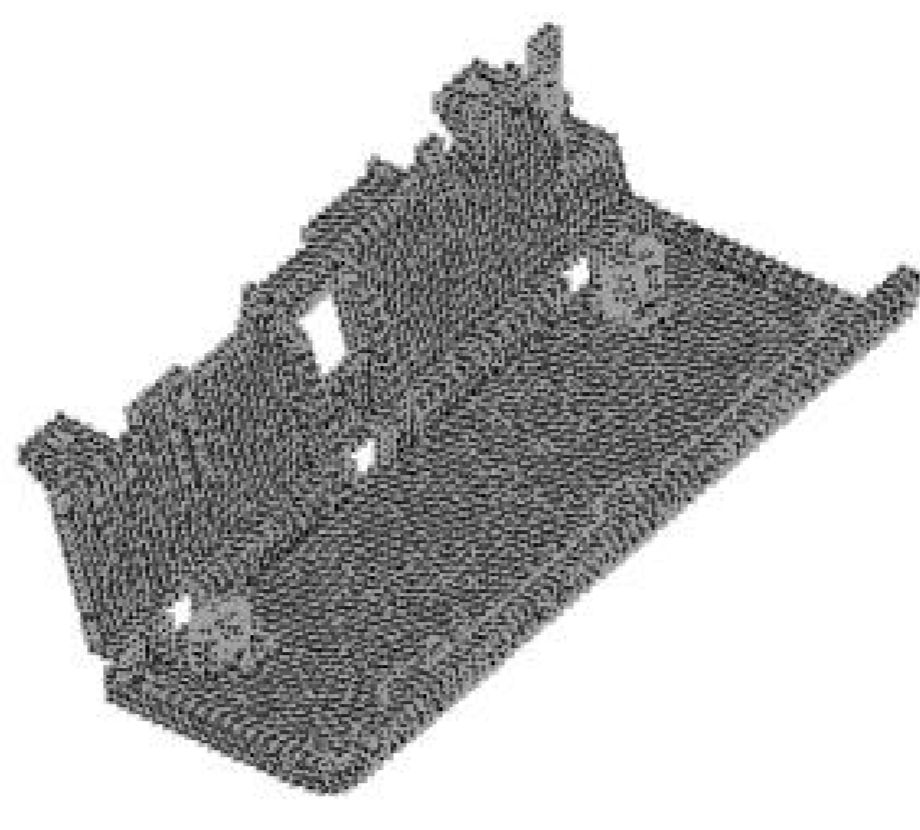


Figure 2. Finite element mesh model

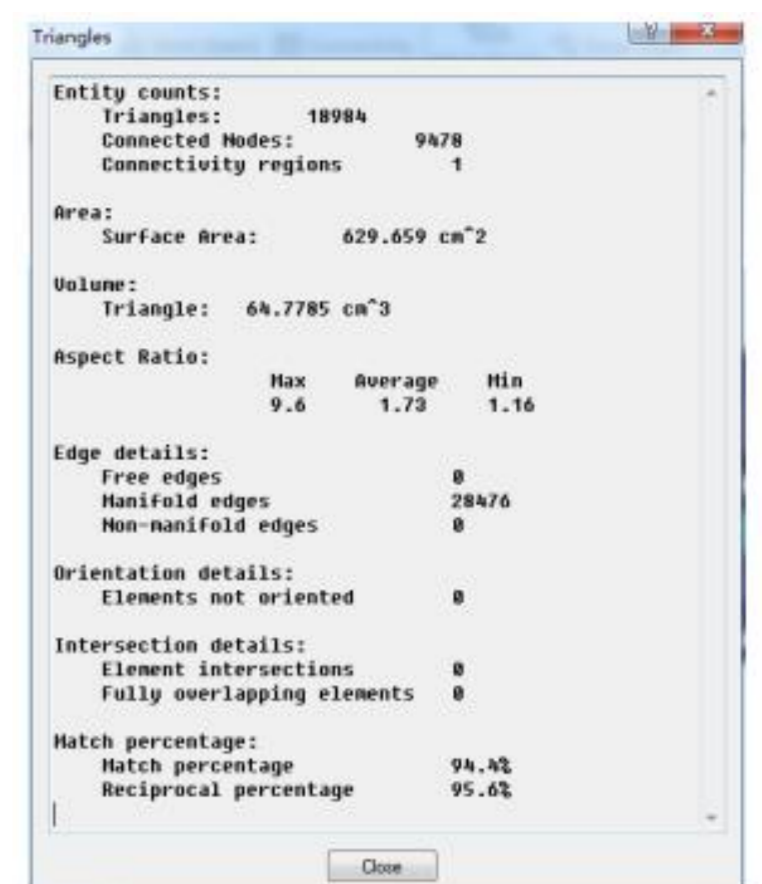


Figure 3. Grid statistics

Fill Analysis

One scheme is one point gate as shown in Figure 4, and the other scheme is two point gates as shown in Figure 5. The diameter of the point gate is 1.8mm. Comparison of analysis results: the filling time of one gate is 1.86 seconds, and the shear rate is: 2.133E+05 - 1, as shown in Figure 6(a); the filling time of two gates is 1.52 seconds, and the shear rate is 29009S⁻¹, as shown in Figure 6(b). Through the analysis results, it can be known that the shear rate of a gate exceeds the maximum shear rate of the material 4000S⁻¹ too much, which may lead to material degradation during the injection molding process. It is better to use two point gates to feed the glue.

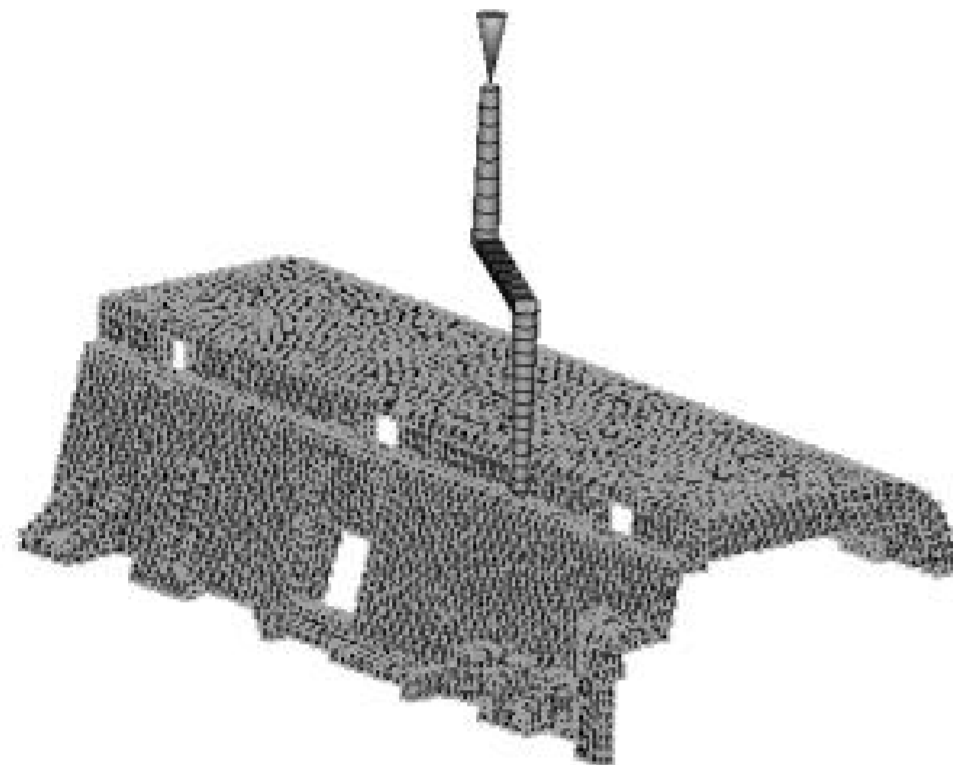


Figure 4. one point gate

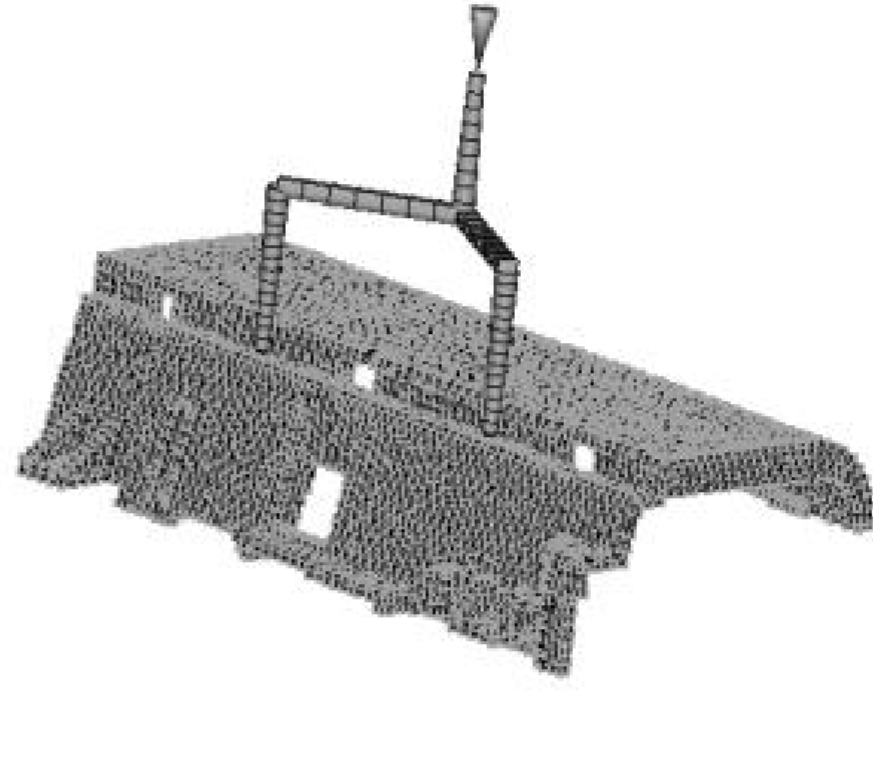


Figure 5. Two point gates

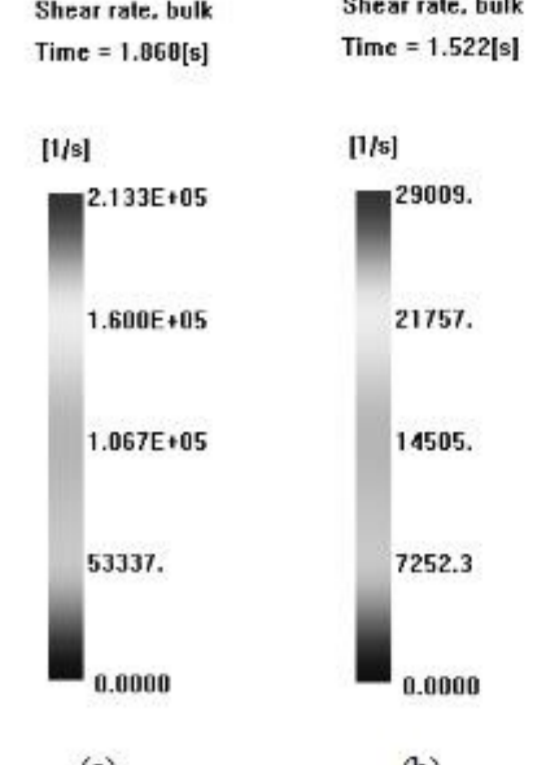


Fig.6 Shear rate

Cooling Analysis

Since the cooling time of the product accounts for 80% of the entire molding cycle, to improve the molding efficiency and shorten the molding cycle, an effective cooling system must be designed. The cooling system also has a great influence on the warpage deformation of the product. Uniform cooling can greatly reduce deformation and improve product quality. Two cooling schemes are developed here for comparative analysis. The first scheme is that the fixed mold part has four cooling water paths, and the movable mold has two "U"-shaped water paths; the second scheme also has four cooling water paths for the fixed mold, and six cooling water paths are designed for the movable mold, including two cooling water paths for the inclined roof. waterway. The total deformation of scheme 1 is 1.116mm, as shown in Figure 7. The total deformation of scheme 2 is 0.7767mm, as shown in Figure 8. It can be clearly seen from the analysis results that the deformation amount of scheme 2 is significantly reduced under the same molding parameters. If the denaturation factor is separated, the deformation amount caused by uneven cooling in scheme 1 is 0.6917mm, as shown in Figure 9, and the deformation amount caused by uneven cooling in scheme 2 is 0.3068mm, as shown in Figure 10. It can be clearly known from the analysis results that the cooling scheme 2 is the best cooling scheme.

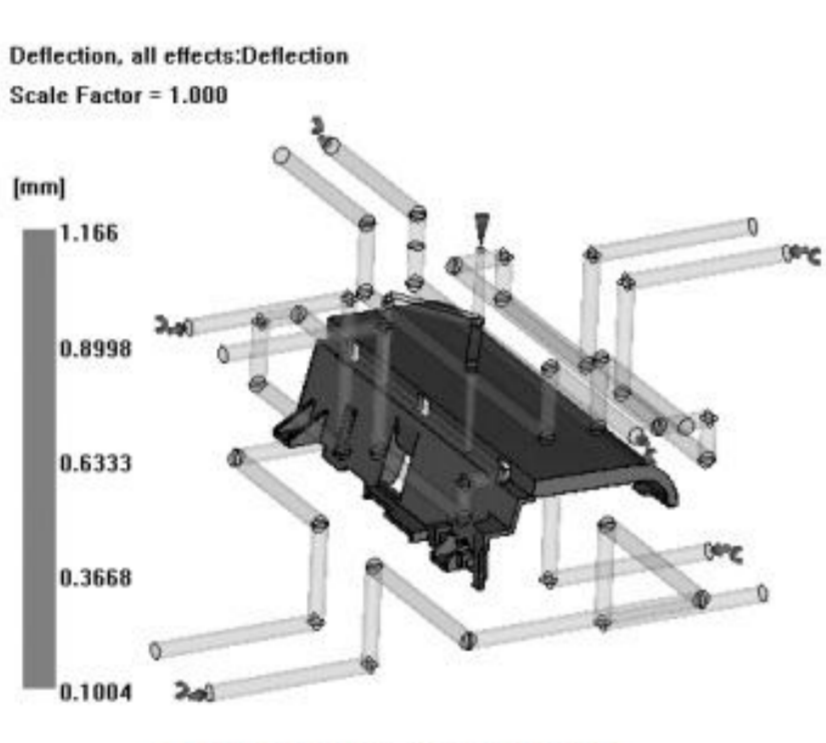


Figure 7. Deformation of scheme 1

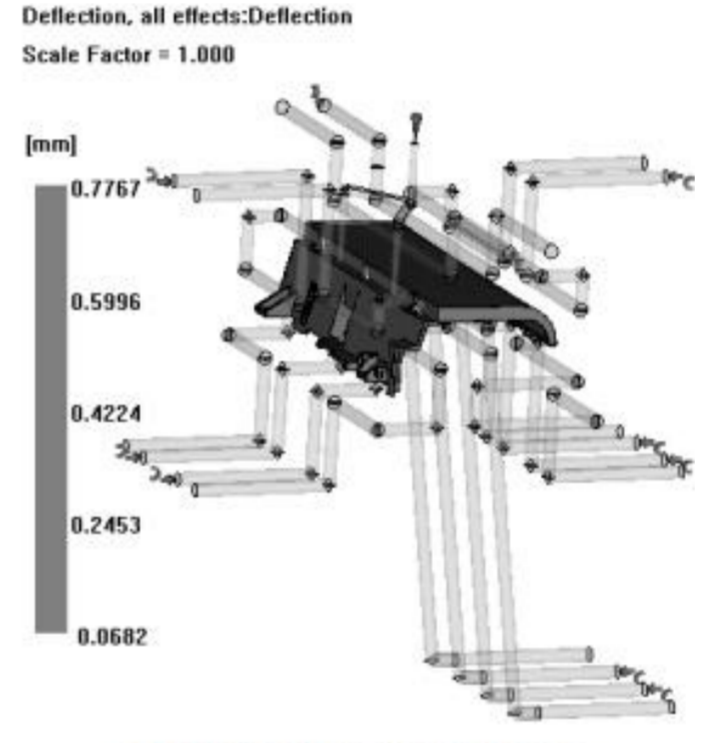


Figure 8. Deformation of scheme 2

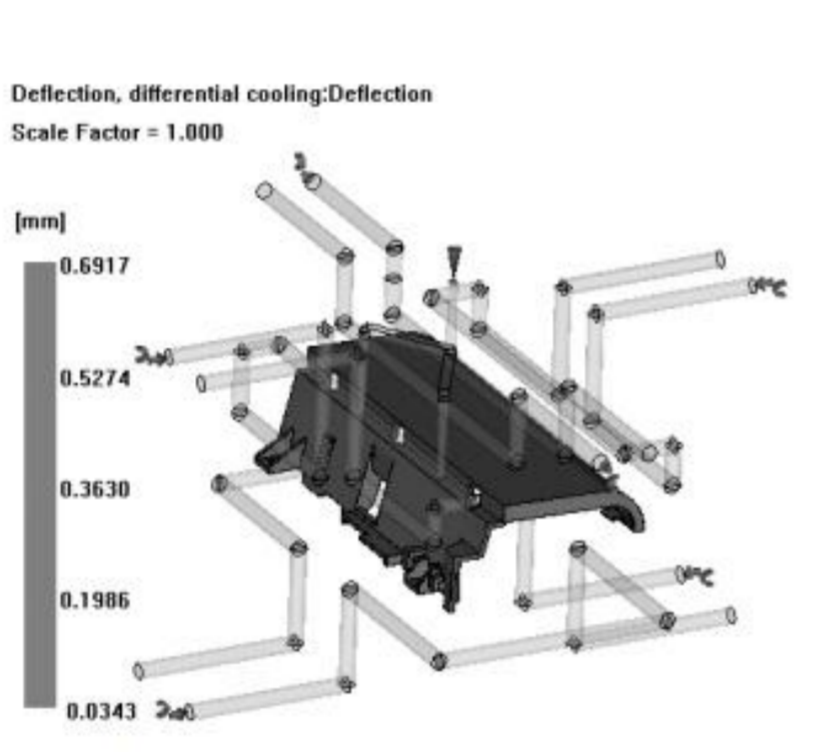


Figure 9. Deformation caused by uneven cooling in scheme 1

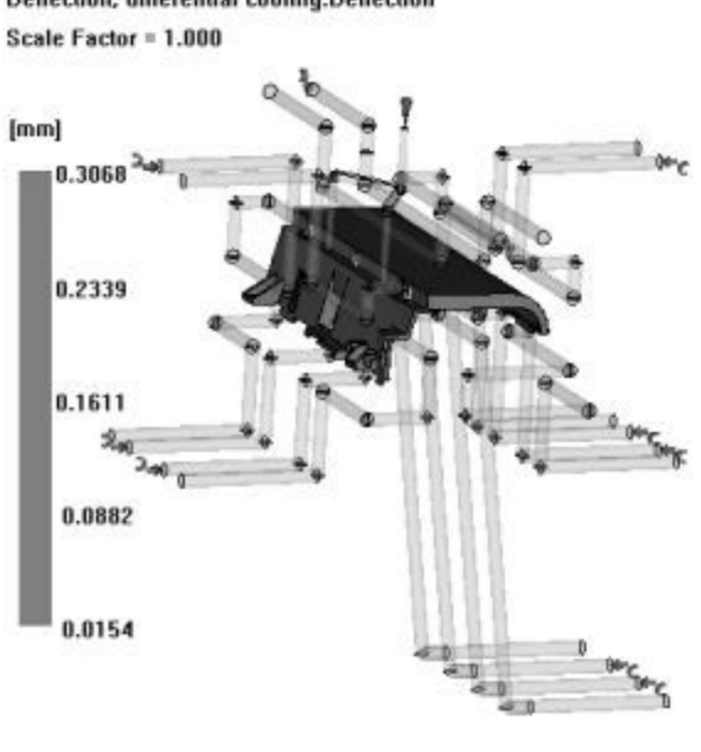


Figure 10. Deformation caused by uneven cooling in scheme 2

Packing pressure analysis

The packing analysis is to obtain the best packing parameters and effectively reduce the warpage deformation of the product. There are four types of pressure holding control methods: % filling pressure and time; holding pressure and time; hydraulic pressure and time; % maximum injection molding machine pressure and time. The default holding pressure method is: % filling pressure and time, and the default holding pressure is 80% of the filling pressure, and the holding pressure time is 10S. Generally, increasing the holding pressure properly can effectively reduce the warpage deformation of the product, but excessive holding pressure will cause the product to over-hold, the residual stress will increase, and a cloak will be formed. The default pressure holding time is often not an effective pressure holding time. The accurate pressure holding time needs to be determined according to the analysis result of the cooling layer factor. The effective pressure holding time is the freezing time of the gate. You can create a new frozen layer factor: XY chart, click the gate location, click the result check button, and then click the first point where the frozen layer factor is 1, you can check that the freezing time of the gate is 8.174S, as shown in Figure 11. Show.

Two pressure holding schemes are formulated based on experience: Scheme 1 is the default holding pressure method and holding pressure parameters, the holding pressure method is "% filling pressure and time", the holding pressure is 80% of the filling pressure, and the holding pressure time is the default 10 seconds. The pressure holding method of scheme 2 is "press holding pressure and time", the holding pressure time is set to two-stage holding pressure, the constant pressure section is 4 seconds, the pressure is 120MP, the time of the decaying pressure holding section is 4 seconds, and the pressure holding section is 4 seconds. The pressure curve is shown in Figure 12. The comparison table of the analysis results of the two pressure-holding schemes is shown in Table 1. The warpage deformation amount, volume shrinkage rate and sink mark of the scheme 2 are smaller than those of the scheme 1, so the pressure-holding scheme 2 is better.

Through the optimization of filling analysis, the optimization of cooling analysis, and finally the optimization of packing. The final warpage analysis results are shown in Figure 13. The maximum deformation of the product is 0.4506mm, which is within the allowable tolerance range of 0.5mm. Meet the product dimensional accuracy requirements.

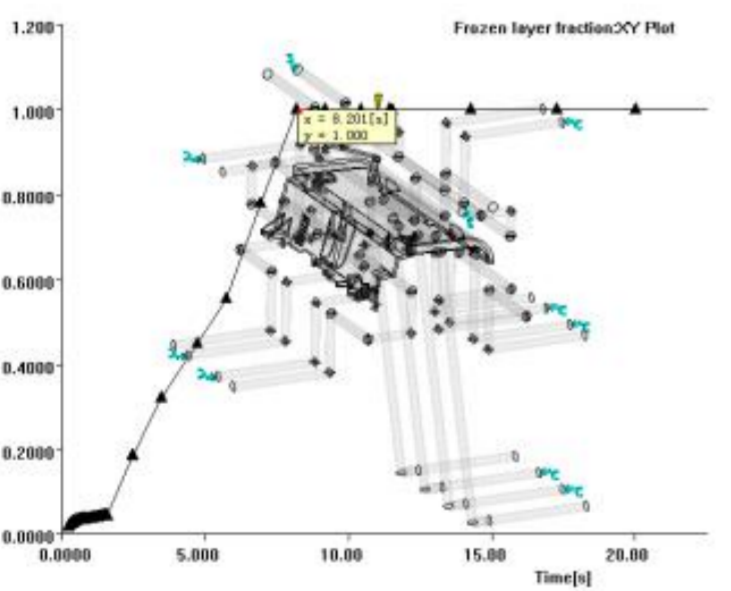


Figure 11. Freezing time of gate

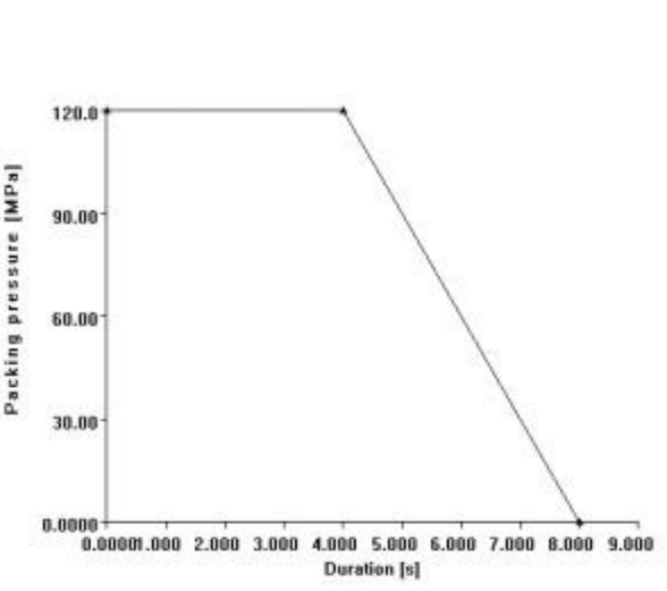


Figure 12. Holding pressure curve

Table 1 Comparison of the analysis results of the two pressure-holding schemes

Analysis results	Plan 1	Plan 2
Warpage deformation	0.7767mm	0.4506mm
Volume shrinkage during ejection	4.626%	1.950%
sink mark, index	2.262%	0.0052%

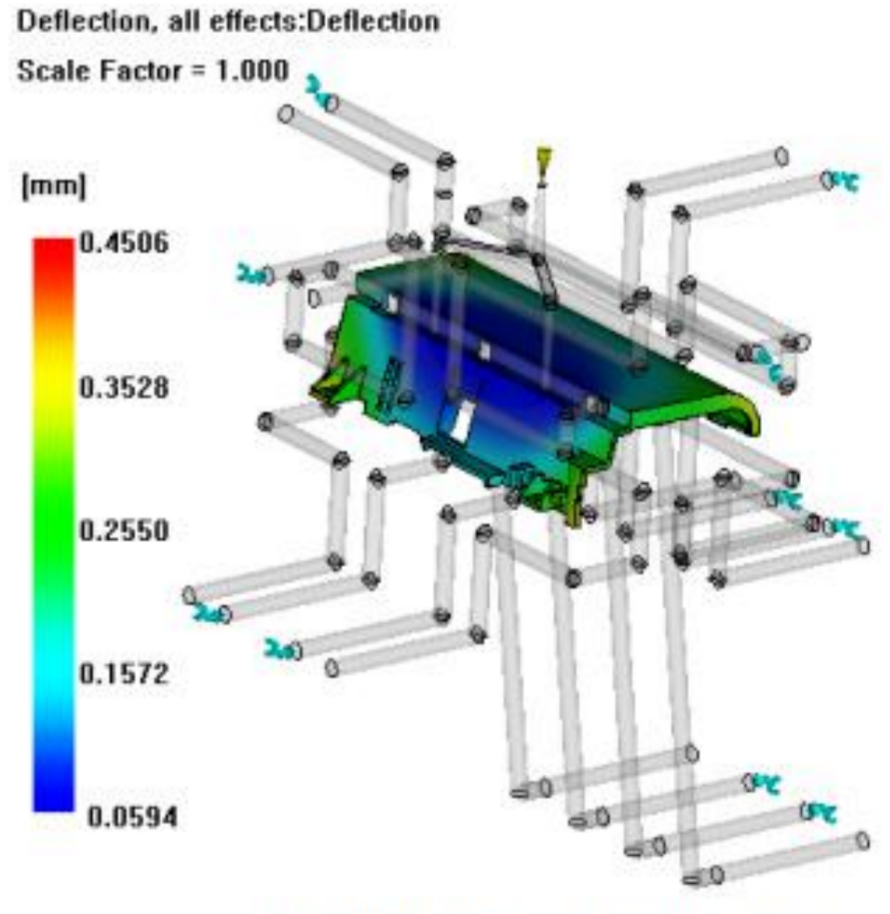


Figure 13. Warpage analysis results

Conclusion

The injection molding analysis of the electromagnetic cover of the digital camera was carried out by Moldflow software. First, the number of gates, the position of the gate, and the size of the gate were optimized through the filling analysis. Then, through cooling analysis, the cooling system is optimized. The fixed mold adopts 4 cooling water paths, and the movable mold includes two cooling water paths for the inclined roof, and a total of 6 cooling water paths are used. Under the premise of the optimization of the previous two, in order to ensure that the warpage deformation of the product is within the allowable dimensional tolerance range, the pressure holding parameters are optimized, and two stages of pressure holding are adopted. The first stage is a 120MP constant pressure for 4 seconds. Pressure holding, the second stage is a decaying pressure holding for 4 seconds, and the maximum warpage deformation of the final product is 0.4506mm, which meets the dimensional accuracy requirements within the allowable dimensional tolerance range. Through the molding simulation analysis, the mold structure design is optimized, the best molding parameters are obtained, the development cycle is shortened, and the enterprise competitiveness is improved.

References

[1]Tan Anping, Liu Kewei . Optimization analysis of warping deformation of automobile glove box cover based on Moldflow [J]. China Plastics, 2019, 33(11): 53-59.
 [2] Miao Ying, Lu Zhonghua, Jin Huajun, Yu Ang. Molding process optimization of combined cavity injection mold based on Moldflow [J]. Plastics Industry, 2019, 47(11): 63-67.
 [3]Ma Yiheng, Wang Xiaoxin, Liu Qin. Design and Process Optimization of Laminated Injection Mold for Washing Machine Balance Ring Based on Moldflow [J]. China Plastics, 2018, 32(7): 132-136.
 [4]Deng Ailin, Xue Song, Xu Bin, et al. Warpage deformation analysis and improvement of guide rails for automobile storage boxes [J]. China Plastics, 2018, 32(1): 125-130.
 [5]Yi Zhibin, Wu Linqian, Wen Hui, et al. Analysis and optimization of injection molding quality of automotive joystick based on Moldflow [J]. Plastics Technology, 2019, 47(6): 72-77.

About the author: Guodong Liang, (1978 -), male, from Guilin, Guangxi, undergraduate, associate professor, mainly engaged in material forming technology and simulation research ; E-mail: 50331624@qq.com.